

PHASE STABILITY OF 3Y-TSZ CERAMICS AFTER DIFFERENT SURFACE TREATMENTS

H. L. Calambras Pulgarin; M.P. Albano ; L.B. Garrido

CETMIC (Centro de Tecnología de Recursos Minerales y Cerámica, CIC-CONICET La Plata)

Camino Centenario y 506. C.C.49 (B1897ZCA) M.B. Gonnet. Buenos Aires. Argentina
e-mail:lgarrido@cetmic.unlp.edu.ar

ABSTRACT

The ability of zirconia ceramics to develop a bioactive surface is of great importance for biomedical applications. For that, it is also required to control phase stability (i.e. to avoid the tetragonal to monoclinic phase transformation) of zirconia surfaces in order to impart a high mechanical resistance. In this work, the phase stability of dense 3 mol% yttria stabilized-zirconia (3Y-TSZ) ceramics after acid and hydrothermal treatments was examined. The zirconia bodies were prepared by slip casting from well dispersed 52 vol% suspensions of 3Y-TSZ, and subsequently sintered to 1300-1500 °C. The effect of various synthesis parameters and 0.25 wt% alumina doping on the phase transformation after acid and hydrothermal treatments was semi-quantitatively evaluated by XRD. The microstructure of the surface layer on the sintered materials was examined by SEM-EDAX.

Keywords: bioceramic, 3Y-TZP; slip casting; phase stability.

INTRODUCTION

The Y₂O₃-stabilized tetragonal ZrO₂ (3Y-TSZ) is an important structural and functional ceramics (1,2). Commonly, these ceramics are produced by the conventional powder processing techniques that involve mixing, pressing and subsequent sintering. Mechanical properties (fracture toughness, strength, and hardness) as well as phase transformation during aging of the final product are strongly dependent on microstructure including the extent of densification, grain size and shape, introduction of an inert material, etc. Through a careful processing a desirable microstructure can be obtained. Colloidal processing is an alternative route to ensure a uniform microstructure

with a reduction in porosity and grain size leading to significant improvements in the ceramic.

The addition of 0.25 wt% of alumina accelerates densification of 3Y-TSZ. The alumina particles locate at the ZrO_2 grain boundaries and change the diffusion sintering mechanism from grain-boundary to volume diffusion preventing grain coarsening (3). Additionally, phase stability of such 3Y-TSZ after hydrothermal treatment may be enhanced.

In this study, dense 3Y-TSZ ceramics were developed by slip casting in a plaster mold and subsequently sintered at different temperatures. The effect of hydrothermal and acid treatments on tetragonal to monoclinic (t-m) phase transformation and microstructure were evaluated by XRD and SEM and compared with that of 0.25 wt% alumina doped ZrO_2 .

EXPERIMENTAL

Materials

Two commercially available ZrO_2 doped with 3 mol% Y_2O_3 stabilized in tetragonal phase (Saint Gobain ZirPro, HanDan) were used. One of these 3Y-TSZ powders was doped with 0.25 wt% alumina (3Y-TSZA) and has a finer average particle size of 0.21 μm whereas that of 3Y-TSZ without alumina was 0.6 μm .

Processing of 3Y-TSZ compacts and sintering

Green compact in a shape of disc (10-12 mm in diameter, 3-4 mm height) was prepared by slip casting. The processing consisted in the preparation of well dispersed aqueous 52 vol% suspensions of 3Y-TSZ by adding to the powder distilled water containing 0.20 wt% of anionic polyelectrolyte dispersant (Dolapix, Zschimmers and Schwartz, Germany). The suspension pH was about 9. After mixing, deagglomeration of the suspension was performed by ultrasonication.

Concentrated aqueous suspension of 3Y-TSZA was prepared using an ammonium polyacrylate solution as a dispersant. Experiments on the dispersion of this alumina doped 3Y-TSZ particle in aqueous solutions have been discussed in a previous work (4).

The resulting suspensions were cast in a plaster mold and then the compact were dried at 100 °C. Green compacts were sintered at temperatures between 1300 and 1500 °C with a heating rate of 5 °C/min and holding time of 2 h. Density of green and sintered compacts was determined using Hg immersion and the water absorption method, respectively. The relative density RD was determined from the ratio between the apparent and theoretical density (6.05 g/cm³).

Surface treatments

The samples were chemically modified with H₃PO₄– 5 M solution at 90 °C for 4 d. Prior to this treatment, the samples were washed in acetone, ethanol and water by ultrasonication. Hydrothermal treatment was performed in an autoclave 134 °C in a water vapor pressure of 2.3 bar (0.2 MPa) with increasing time up to 10 h.

Characterization methods

Crystalline phase composition of sintered surfaces were examined by XRD (Philips 3020 equipment) with Cu-K α radiation in Ni filter at 40 kV–20 mA. The relative proportions of both monoclinic and stabilized phases were semi-quantitatively determined by XRD analysis using the Garvie and Nicholson method (5) and then the relative volume fraction of m-ZrO₂ was calculated (6).

Microstructure of the sintered compacts was observed by a scanning electron microscope SEM (FEI Quanta 200 MK2 Serie) and microanalysis (EDX) using the polished surface of the sintered ceramics (transversal section).

RESULTS AND DISCUSSION

The relative density of green compacts produced from well dispersed suspension by slip casting was approximately 0.628. The relative density of 3Y-TZP compacts sintered at 1300°C increased to 0.88, and higher densification of 0.98 achieved at 1400°C. Both 3Y-TSZ and 3Y-TSZA compacts exhibited nearly full densification at 1500°C. Thus open porosity reduced at 1400 °C and most pores were closed.

The X-ray diffraction patterns (Fig. 1) of 3Y-TSZ confirmed that it mainly consists in tetragonal phase but in the 2 θ range from 27 to 32 ° a trace of monoclinic phase was

detected for all samples. According to Fig. 2 a minor amount of cubic phase formed after sintering at 1500 °C.

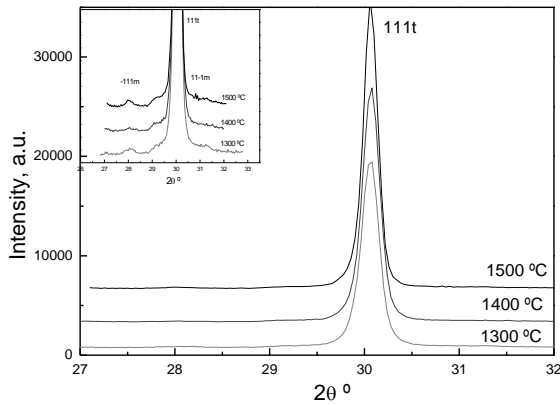


Figure1. XRD patterns of 3Y-TZP sintered at different temperatures. Detail showing trace of monoclinic phase.

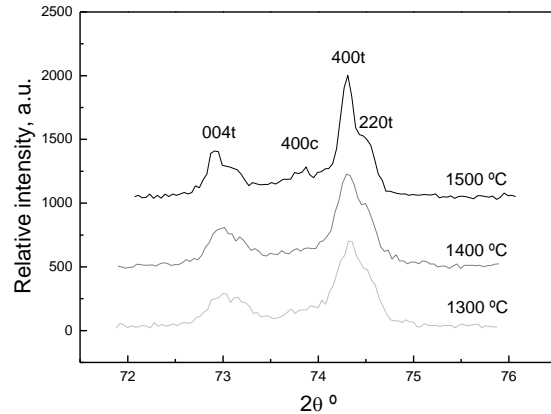


Figure 2. XRD patterns in the 2θ range 72-74° for 3Y-TZP sintered at different temperatures.

The existence of cubic phase in 3Y-TSZ ceramics stabilized in tetragonal was previously confirmed by XRD (7, 8). Matsui et col. (9) showed that relative content of cubic phase attained up to 12.7 and 18.6 wt% for 1300 and 1500 °C, respectively and it correlated with the distribution of the Y^{3+} ions inside the zirconia grains, which depends on several processing conditions such as sintering temperature. Particularly, this study shows that Y^{3+} ions resulted homogeneously distributed in most grains of the compact sintered at 1300 °C, whereas a higher amount Y^{3+} ions appeared to concentrate within large grains after sintering at 1500 °C. Therefore, the formation of cubic phase started to originate in certain regions at which Y^{3+} ions had segregated (i.e. grain boundaries and triple junctions).

Effect of hydrothermal treatment on phase stability

The transformation rate at which the tetragonal phase is transformed to monoclinic phase is an indication of the hydrothermal sensitivity of the ZrO_2 containing ceramics. The effect of hydrothermal treatment on phase stability of dense 3Y-TSZ casts sintered at different temperatures was examined. The evolution of XRD patterns with time after hydrothermal treatment for all samples was determined, but only the increase in

monoclinic peak intensity corresponding to 3Y-TSZA (doped with 0.25 wt% alumina) sintered at 1500 °C is showed in Fig. 3.

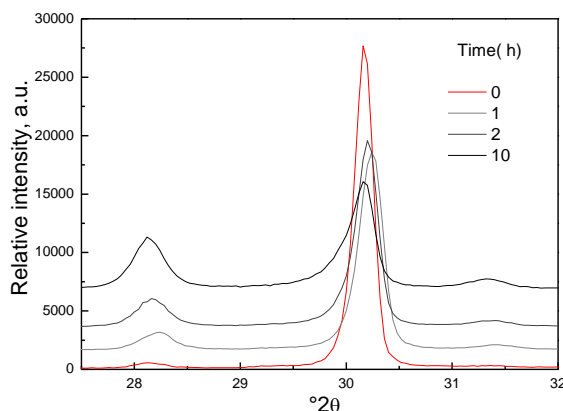


Figure 3. XRD patterns of 0.25 wt % alumina doped 3Y-TSZ after hydrothermal treatment at different times. a: 0, b: 1, c: 2, d: 10 h.

Fig. 4 shows the variation of the volume fraction of monoclinic phase with time for the different 3Y-TSZ samples with and without alumina doping.

Only scarce content of monoclinic fraction was detected for 3Y-TSZ sintered at 1300 °C after hydrothermal treatment up to 10 h. For curves of samples sintered at 1400 °C the volume fraction of monoclinic phase remained very low for times below 2h and then increased up to 0.35 after 10 h. At 1500 °C, the curves show a nearly sigmoid shape in which the monoclinic content slowly increased at low and high times and it increased rapidly at an intermediate time. In this case, the relative monoclinic fraction reached 0.2 for 1 h resulting in a higher content than those of the other samples. This sample exhibited the lower phase stability as transformation started at times lower than 1h; the curve also presented a much higher slope and thus the intermediate part of the curve appeared for times >1 h, for that the monoclinic volume fraction approximated to 0.45 for 10 h. This rapid degradation behavior was consistent with the presence of cubic phase detected by XRD (Fig. 2).

The relation between cubic phase and accelerated aging in 3mol% yttria-stabilized zirconia was previously found. Previous works (2, 7-9) indicated that phase stability of

sintered 3Y-TSZ to hydrothermal treatment improved with reducing porosity and grain size.

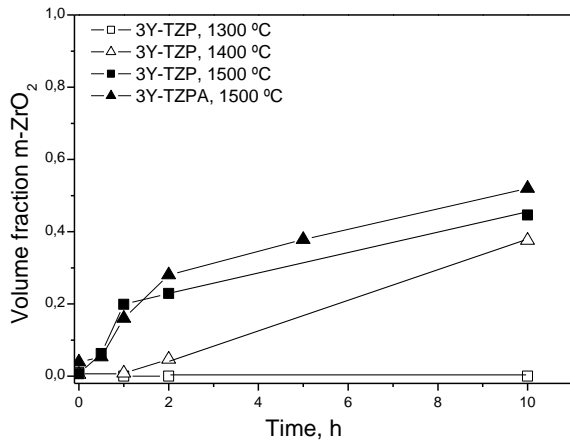


Figure 4. Volume fraction of monoclinic phase vs. time for 3Y-TZP sintered at different temperatures and 3Y-TZPA doped with 0.25 wt% alumina sintered at 1500 °C.

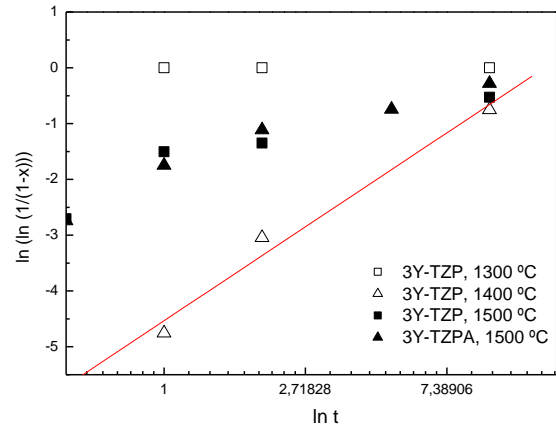


Figure 5. $\ln(\ln(1/(1-x)))$ vs. $\ln t$ using experimental data of Fig.4

There is a critical grain size of 0.3 μm for 3 mol% yttria content of stabilizing agent below which phase transformation does not occur. Therefore, a good combination between high sintering temperatures to attain high densification and that required to avoid an increase in the grain size as well as heterogeneity in Y distribution may be favorable to retain t-ZrO₂.

Previous studies suggested a nucleation and growth kinetics to describe the variation of monoclinic volume fraction x with time (2, 7, 9-11). The model equation contain two parameters which can be derived from the linearized $\ln(\ln(1/(1-x)))$ vs. $\ln t$. The Fig. 5 shows the approximately linear relation, from which the exponent n and a parameters involved in the model equation (2,7,9-11) can be obtained. The calculated results using experimental data of sample sintered at 1400 °C are shown by a line in Fig. 5. The resulting parameter n near to 1.70 was lower than that expected value of $\sim 3-4$ considering that phase transformation proceeds via homogeneous nucleation and growth mechanism (10). However, the n value between 1 and 2 corresponded well to a nucleation and one-dimensional growth process (3). The samples sintered at 1500 °C

exhibited a reduction in the slope (i.e. a low n value). According to (12), the low n value suggested a different mechanism in which nucleation predominated and growth proceeded at slower rates. There was not a clear indication that alumina doping provided high phase stability as was previously reported for small amount of silica doping on 3Y-TSZ ; this difference can be attributed to a low grain size of $0.55 \mu\text{m}$ (3).

Effect of hydrothermal treatment on microstructure of exposed surface

SEM micrographs revealed a dense microstructure of the sintered ceramic (transversal section), with some isolated and closed pores (Fig. 6) .

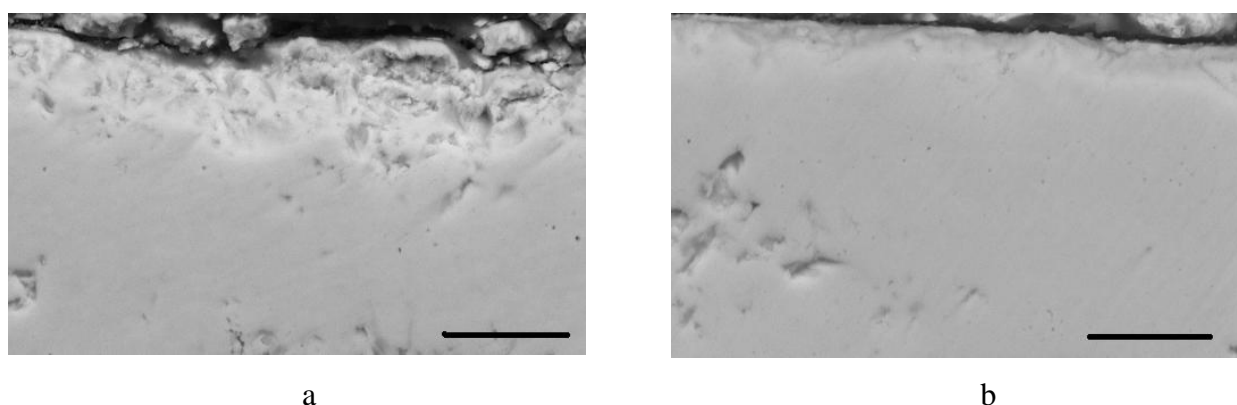


Figure 6. SEM micrographs of transversal section of 3Y-TSZ showing surface layer (upper part) after hydrothermal aging -2h. a: 1400 C ; b: 1500 . (Bar: $10 \mu\text{m}$)

An increase in porosity, roughness and deterioration of the exposed surface was clearly observed as a result of transformation to monoclinic phase (volume fraction ~ 0.15).

Effect of acid treatment on phase stability

Figures 7 and 8 show the effect of the acid treatment on phase stability for 3Y-TSZ sintered at different temperatures and that doped with 0.25 wt% alumina sintered at $1500 \text{ }^{\circ}\text{C}$. XRD patterns of samples after acid treatment showed the decrease of tetragonal peak intensity and the increase of monoclinic one with sintering temperature indicating the t to m phase transformation. The highest phase transformation after acid treatment was found in the 3Y-TSZ sintered at 1400 and $1500 \text{ }^{\circ}\text{C}$ as monoclinic volume fraction resulted close to 0.83 compared with 0.62 for compacts sintered at $1300 \text{ }^{\circ}\text{C}$. Although in the latter, more pore surface was exposed to acid, high porosity did not

correlate with the results of phase transformation. Monoclinic content of these samples in acid solution was higher than those after hydrothermal treatment (vol. fraction ~0.44).

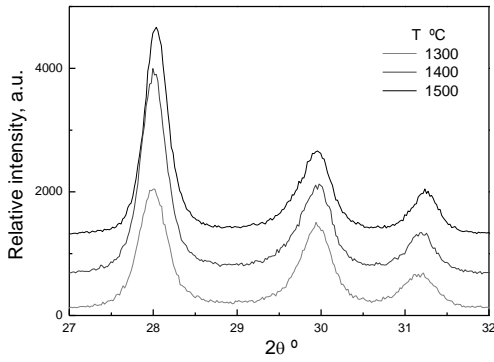


Figure 7. XRD patterns of 3Y-TSZ sintered at different temperatures after acid treatment.

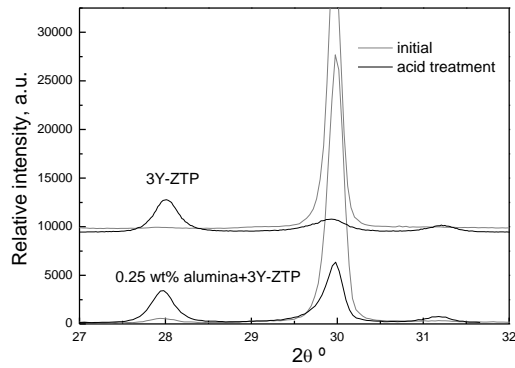


Figure 8. XRD patterns of 3Y-TSZ and that doped with 0.25 wt% alumina sintered at 1500°C and after acid treatment

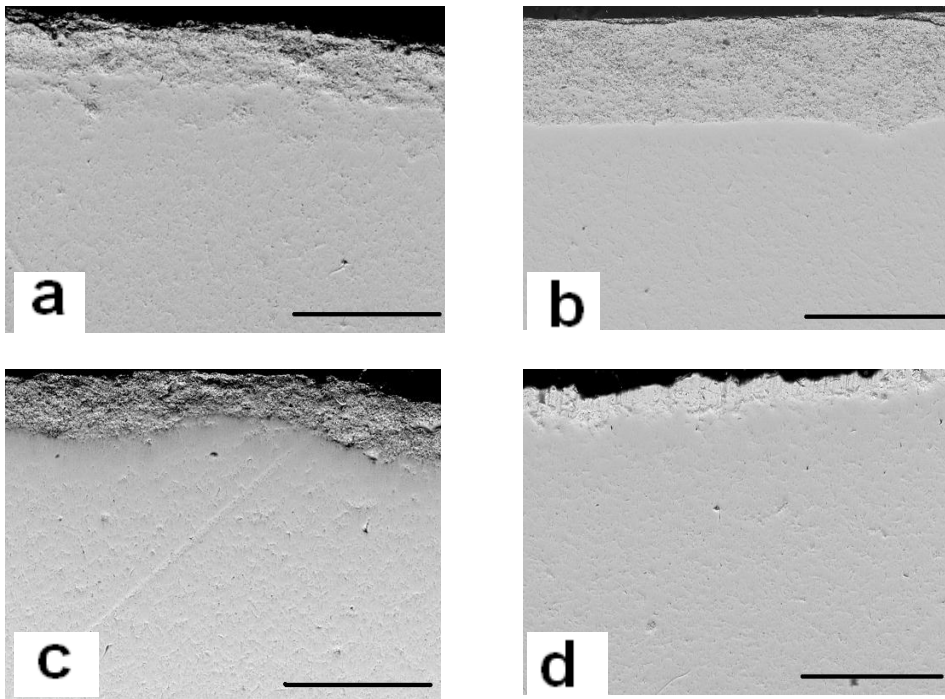


Figure 9. SEM micrographs of transversal section of 3Y-TSZ showing surface layer after acid treatment for different sintering temperatures. a: 1300 ; b: 1400 ; c: 1500; d: 1500 C (top surface), Bar: 100 µm.

Negligible amount of m-ZrO₂ phase was initially found in 3Y-TSZA sintered at 1500 °C but the volume fraction of this sample increased to 0.53 after acid treatment which is a relatively low value as compared with the other samples. Fig. 9 show that the microstructural modification below the 3Y-TSZ surface after acid treatment progressed with increasing temperature. For samples sintered at 1500 °C, however a different behavior was found between the surface which was in contact with the plaster mold and the top surface of the sintered compacts (Fig. 9 c and d, respectively). Below the top surface, a layer with small thickness was observed. The top surface of this ceramic before treatment was smooth and brilliant that implies the presence of very fine particles causing a positive effect on resistance to acid treatment.

CONCLUSIONS

Phase stability of dense 3Y-TSZ with and without 025 wt% alumina doping processed by slip casting after hydrothermal treatment and in phosphoric acid was examined. The processing conditions have a critical role on phase stability. Sintering at temperatures below 1400 °C limited the t to m phase transformation of 3y-TSZ surface after 10 h of hydrothermal treatment but microstructure of exposed surface appeared more deteriorated. On the contrary, such treatment led to marked increase in the phase transformation of samples sintered at 1500°C which contained scarce cubic phase. Similar effects caused the acid treatment. For 3Y-TSZ sintered at 1500 °C , the volume fraction of m-ZrO₂ exceeded the respective value found after treatment in autoclave 10 h. Doping with alumina was more effective to improve resistance to phase transformation by treatment in phosphoric acid.

REFERENCES

1. HANNINK, R. H.; KELLY, P. M.; MUDDLE, B.C. Transformation Toughening in Zirconia-Containing Ceramics. J. Am. Ceram. Soc., v. 83, n. 3, p. 3461–3487, 2000.
2. KELLY, R. J.; DENRY, I. Stabilized zirconia as a structural ceramic: An overview. Dental materials, v.2, n.4, p.289–298, 2008.

3. TAKIGAWA, Y.; SHIBANO, T.; KANZAWA, Y.; HIGASHI, K. Effect of small amount of insoluble dopant on tetragonal to monoclinic phase transformation in tetragonal zirconia polycrystal.
Materials Transactions, v. 50, n. 5, p.1091-1095, 2009.
4. CALAMBAS PULGARIN, H. L.; GARRIDO, L.B.; ALBANO M.P.; Rheological properties of aqueous alumina–alumina-doped Y-PSZ suspensions.
Ceram. Int., v. 38, n.3, p.1843–1849, 2012.
5. GARVIE, R.C.; NICHOLSON, P.S. Phase analysis in zirconia systems.
J. Am. Ceram. Soc. v.55, n. 2, p. 303–305, 1972.
6. DEHESTANI, M.; ADOLFSSON, E. Phase Stability and Mechanical Properties of Zirconia and Zirconia Composites.
Int. J. Appl. Ceram. Technol., v.10, n. 1, p.129–141, 2013.
7. CHEVALIER, J.; DEVILLE, S.; MUNCH, E.; JULLIAN, R.; LAIR, F. Critical effect of cubic phase on aging in 3 mol% yttria-stabilized zirconia ceramics for hip replacement prosthesis.
Biomaterials, v.25, n.24, p. 5539–5545, 2004.
8. KUBO, T.; ICHIKAWA, K.; MACHIDA, N.; SAKAI, H.; SHIGEMATSU, T. Effect of calcining temperature on the tetragonal-to-monoclinic phase transition characteristics in 2 mol% Yttria-doped zirconia ceramics.
J. Mat. Sci., v.35, n.12, p. 3053-3057, 2000.
9. MATSUI, K.; HORIKOSHI, H.; OHMACHI, N.; OHGAI, M.; YOSHIDA, H.; IKUHARA, Y. Cubic-formation and grain-growth mechanisms in tetragonal zirconia polycrystal.
J. Am. Ceram. Soc., v.86, n.8, p.1401–1408, 2003.
10. CHEVALIER, J.; CALES, B.; DROUIN, J.M. Low-temperature aging of Y-TZP ceramics.
J. Am. Ceram. Soc., v.82, n.8, p.2150–2154, 1999.
11. YASUDA, K.; GOTO, Y.; TAKEDA, H. Influence of tetragonality on tetragonal-to-monoclinic phase transformation during hydrothermal aging in plasma-sprayed yttria-stabilized zirconia coatings.
J. Am. Ceram. Soc., v.84, n. 5, p.1037-1042, 2001.
12. GREMILLARD, L.; CHEVALIER, J.; EPICIER, T.; DEVILLE S.; FANTOZZI, G. Modeling the aging kinetics of zirconia ceramics.
J. Europ. Ceram. Soc., v. 24, n. 13, p. 3483-3489, 2004.